

Integrated sensing for ionic polymer–metal composite actuators using PVDF thin films

This article has been downloaded from IOPscience. Please scroll down to see the full text article.

2007 Smart Mater. Struct. 16 S262

(<http://iopscience.iop.org/0964-1726/16/2/S10>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 156.26.43.24

The article was downloaded on 30/08/2013 at 23:15

Please note that [terms and conditions apply](#).

Integrated sensing for ionic polymer–metal composite actuators using PVDF thin films

Zheng Chen¹, Yantao Shen², Ning Xi² and Xiaobo Tan^{1,3}

¹ The Smart Microsystems Laboratory, Department of Electrical and Computer Engineering, Michigan State University, East Lansing, MI 48824, USA

² The Robotics and Automation Laboratory, Department of Electrical and Computer Engineering, Michigan State University, East Lansing, MI 48824, USA

E-mail: chenzhe1@egr.msu.edu and xbtan@msu.edu

Received 16 June 2006, in final form 17 July 2006

Published 9 March 2007

Online at stacks.iop.org/SMS/16/S262

Abstract

Compact sensing methods are desirable for ionic polymer–metal composite (IPMC) actuators in microrobotic and biomedical applications. In this paper a novel sensing scheme for IPMC actuators is proposed by bonding an IPMC and a PVDF (polyvinylidene fluoride) thin film with an insulating layer in between. The insulating layer thickness is properly designed to minimize the stiffness of the composite IPMC/PVDF structure while reducing the electrical feedthrough coupling between the IPMC and PVDF. A distributed circuit model is developed to effectively represent the electrical coupling dynamics, which is then used in real-time compensation for extraction of the true sensing signal. Experimental results show that the developed IPMC/PVDF structure, together with the compensation algorithm, can perform effective, simultaneous actuation and sensing. As the first application, this sensori-actuator has been successfully used for performing and monitoring open-loop micro-injection of living *Drosophila* embryos.

(Some figures in this article are in colour only in the electronic version)

1. Introduction

Ionic polymer–metal composites (IPMCs) form an important category of electroactive polymers which have both built-in actuation and sensing capabilities [1, 2]. Due to their large bending displacement, low driving voltage, resilience, and biocompatibility, IPMCs have been explored for potential applications in biomimetic robotics [3, 4], medical devices [5], and micromanipulators [6–8]. In most of these applications, *compact* sensing schemes are desired for feedback control of IPMC actuators to ensure precise and safe operation without using bulky, separate sensors. It is intriguing to utilize the inherent sensory property of an IPMC to achieve simultaneous actuation and sensing, like the self-sensing scheme for piezoelectric materials [9]. However, this approach is difficult to implement due to the very small magnitude of the sensing signal compared to the actuation signal (millivolts versus volts) [2] and the nonlinear [10], dynamic [11] sensing responses. Newbury [12] explored the idea of using two

IPMCs, mechanically coupled in a side-by-side or bilayer configuration, to perform actuation and sensing. The attempt was reported to be unsuccessful since the sensing signal was buried in the feedthrough signal from actuation [12].

In this paper, to our best knowledge, we are the first to report the integration of a highly actuating IPMC and highly sensitive PVDF for simultaneous actuation and sensing. PVDF is a flexible piezoelectric polymer widely used as sensors and actuators [13]. Although a sensori-actuator made of PVDF alone has been developed in [14, 15], its application to microsystems and biomedical systems is limited due to the high actuation voltage (over 40 V), as opposed to the low actuation voltage (under several volts) needed for an IPMC. The thin, soft PVDF layer provides a strong sensing signal while having a minimal impact on the IPMC bending performance. However, the electrical feedthrough from the IPMC actuation signal to the PVDF sensing signal, arising from the proximity of the IPMC and PVDF, presents a significant challenge in real-time extraction of the sensing signal. A thicker insulating layer would

³ Author to whom any correspondence should be addressed.

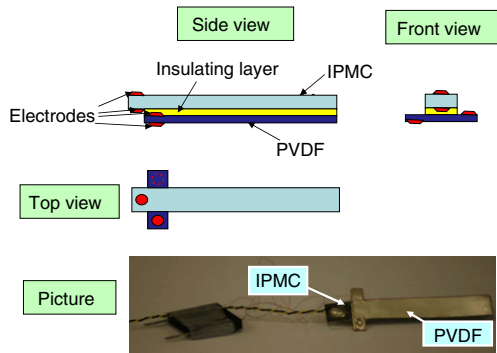


Figure 1. Design of the IPMC/PVDF composite structure.

lead to weaker feedthrough coupling, but at the cost of reduced actuation displacement due to the increased structural stiffness. The stiffening effect caused by the PVDF and insulating layers is investigated through analytic modeling, finite-element computation and experimental measurement. Good agreement is achieved between analysis, computation and experiments on the impact of the insulating layer thickness on the IPMC/(insulator)/PVDF structural stiffness. Based on these results, the insulating layer thickness is properly chosen for sound trade-off between minimization of structural stiffness and that of electrical feedthrough.

The electrical feedthrough is still not negligible for the chosen insulator thickness. To fully account for the effect of the feedthrough coupling, we develop a distributed circuit model for the IPMC/(insulator)/PVDF structure. The circuit parameters are determined based on impedance measurement through a nonlinear fitting process. Comparison between PSpice⁴ simulation and experimental measurement shows that the model represents the feedthrough coupling dynamics well. A real-time compensation scheme is then implemented using a reduced feedthrough model to extract the correct sensing signal.

As a biological application, the IPMC/PVDF structure is being investigated for automating the process of *Drosophila* embryo injection. Genetic modification of *Drosophila* embryos not only provides scientifically interesting insights, but also offers an understanding of biological mechanisms to cure diseases [16]. One of the most important tasks in genetic modification is the injection of substances that affect the makeup of a cell or an organism. Most embryo injections are currently conducted manually, and the success rate is quite low (about 2–4%). As a first step toward the goal of fully automated injection, the proposed IPMC/PVDF structure is used to deliver and monitor the penetration of the *Drosophila* embryo in an open-loop manner.

The remainder of the paper is organized as follows. The design of the IPMC/PVDF structure and the sensing circuit is described in section 2. The impact of the stiffening effect due to the PVDF and insulator layers is studied in section 3. The modeling and compensation methods for the feedthrough coupling phenomenon are presented in section 4. The experimental setup and results for the micro-injection of living *Drosophila* embryos are shown in section 5. Finally, the work is concluded in section 6.

⁴ http://www.cadence.com/products/si_pk_bd/pspice_a_d/index.aspx

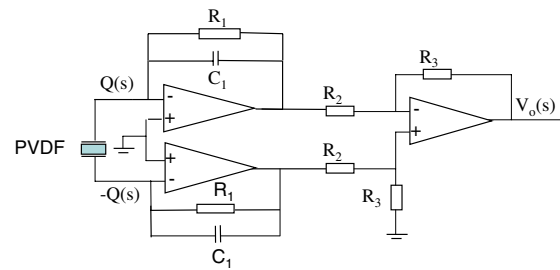


Figure 2. Design of the charge amplifier.

2. Design of IPMC/PVDF structure and sensing circuit

2.1. IPMC/PVDF structure and sensing circuit

To construct the IPMC/PVDF sensori-actuator, a PVDF film (30 μm thick, Measurement Specialties Inc.) is bonded to an IPMC (340 μm thick, Environmental Robotics Inc.) with an insulating layer (polyvinyl chloride (PVC) film, 30 μm thick) in between. A fast-cure elastic epoxy (Polysciences Inc., Warrington, PA) is used in bonding. The design of the IPMC/PVDF structure is illustrated in figure 1, where a picture of the IPMC/PVDF prototype is shown at the bottom.

An IPMC using water as solvent needs to be hydrated to work in air. For the IPMC/PVDF structure, it is not recommended to immerse the sample in water due to the presence of the PVDF. Instead, one can place a damp paper towel on top of the IPMC side of the structure and at the same time apply a uniform compressive stress. This will facilitate uniform hydration of the IPMC while preventing the delamination of the layers. The selected PVDF film has high stability and strong capabilities to resist moisture (<0.02% moisture absorption) and most chemicals [17]. All the electrodes of the IPMC and PVDF are well insulated and aligned without short circuit during the hydration. Following these properties and facts, the effect of the humidity level on PVDF sensing is not observed to be appreciable. The hydrating procedure is not required if one adopts IPMC samples that use ionic fluids [18] or other non-water-based solvents.

When the IPMC/PVDF structure is bent due to IPMC actuation or external forces, charges are generated on the PVDF, which can be measured by a charge amplifier. Figure 2 shows a differential charge amplifier which can minimize the common-mode noise. The transfer function of the charge amplifier is described by

$$\frac{V_o(s)}{Q(s)} = \frac{2R_1s}{1 + R_1C_1s} \frac{R_3}{R_2}, \quad (1)$$

which is a high-pass filter. As $R_1 \rightarrow \infty$, the transfer function $\frac{V_o(s)}{Q(s)} \rightarrow \frac{2R_3}{C_1R_2}$. However, in the circuit implementation, R_1 cannot be infinitely large because the bias current of the operational amplifier will saturate the signal output. To accommodate the actuation bandwidth of the IPMC (typically below 10 Hz), the R_1 and C_1 values in the circuit are properly chosen so that the cut-off frequency of the charge amplifier is sufficiently low. By picking $R_1 = 5000 \text{ M}\Omega$ and $C_1 = 1350 \text{ pF}$, a cut-off frequency of 0.023 Hz is achieved.

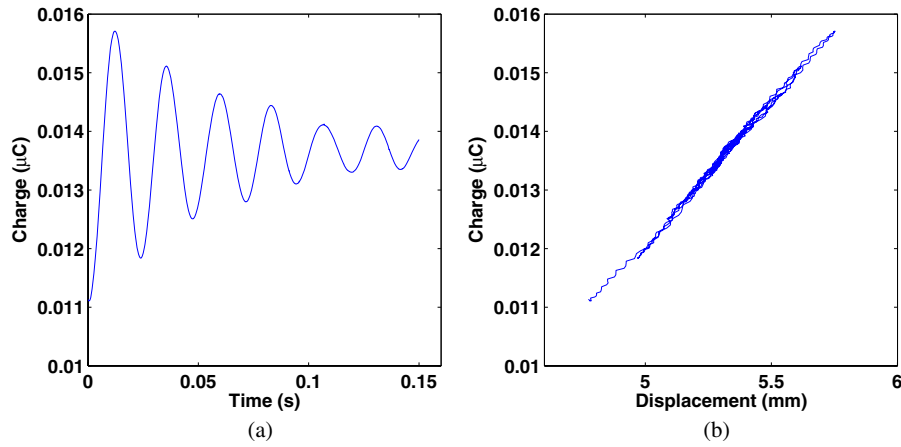


Figure 3. (a): Charge output of the PVDF corresponding to the damped vibration; (b): charge output versus the bending displacement.

Basically, the charge $Q(s)$ generated by the PVDF is proportional to the bending displacement $Z(s)$ of the beam [19]:

$$Q(s) = GZ(s), \quad (2)$$

where the constant G depends on the transverse piezoelectric coefficient d_{31} , the geometry of the composite beam and the Young’s moduli of individual layers. By combining (1) and (2), one can obtain the transfer function from $Z(s)$ to $V_o(s)$. A laser displacement sensor (OADM 2016441/S14F, Baumer Electric) is used for both calibration of the PVDF sensor and validation of the sensing approach. In order to test the charge amplifier circuit, the IPMC/PVDF beam with one end fixed is tapped and then the laser sensor is used to detect the damped vibration of the beam. The measured vibration frequency is 42 Hz, which is much higher than the cut-off frequency of the charge amplifier. Figure 3(a) shows the charge output of the PVDF corresponding to the damped vibration, and figure 3(b) demonstrates that the charge signal is almost linear with respect to the bending displacement. These experimental results have validated the performance of the charge amplifier circuit.

3. Impact of the stiffening effect and design of the insulator thickness

The additional PVDF and insulating layers make the composite beam stiffer than the IPMC layer itself. It is of interest to understand the impact of this stiffening effect on the bending performance since this will be useful for the optimal IPMC/PVDF structure design. The investigation is conducted by combining analytical modeling, finite element computation and experiments. Design optimization here is concentrated on the thickness of the insulating layer, but the approach can be used for the design of other parameters, such as the type of material for the insulating layer and the dimensions for the IPMC and PVDF.

Figure 4 illustrates the schematic of the IPMC/PVDF structure and the notation used in the following discussion. The beam stiffness can be characterized by its spring constant

$$K = \frac{F}{z_{\max}}, \quad (3)$$

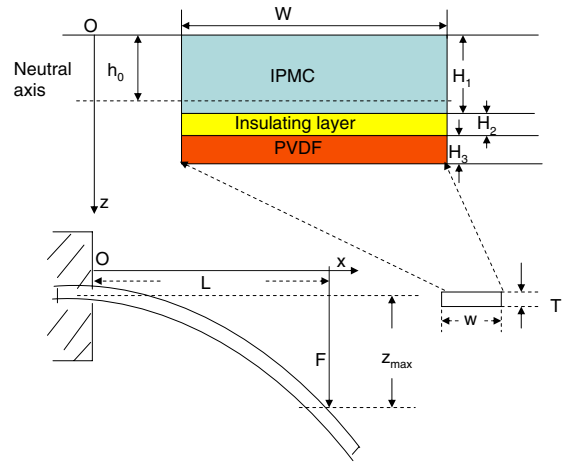


Figure 4. Bending of IPMC/PVDF composite beam.

where F is a quasi-static transverse force applied at the free end of the cantilever beam and z_{\max} is the corresponding displacement at the acting point. The spring constant can be calculated analytically using composite beam theory [20]. In figure 4, the position of the mechanical neutral axis of the composite beam is given by

$$h_0 = \frac{\sum_{i=1}^3 E_i H_i C_i}{\sum_{i=1}^3 E_i H_i}. \quad (4)$$

Here E_1 , E_2 and E_3 are the Young’s moduli of the IPMC, insulating layer and PVDF, respectively. H_1 , H_2 and H_3 are the thicknesses of those layers. C_1 , C_2 and C_3 are the positions of the central axes of the layers, which can be calculated as

$$\begin{aligned} C_1 &= H_1/2, & C_2 &= H_1 + H_2/2, \\ C_3 &= H_1 + H_2 + H_3/2. \end{aligned} \quad (5)$$

The distance between the central axis and the neutral axis can be written as

$$d_i = |C_i - h_0|, \quad \text{for } i = 1, 2, 3. \quad (6)$$

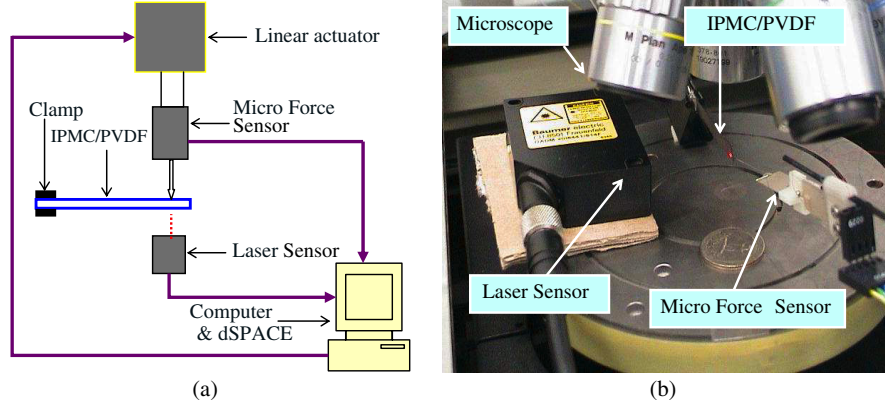


Figure 5. (a) Experimental setup for spring constant measurement; (b) picture of the experimental setup.

Table 1. Dimensions and spring constants of different beams.

Beams	IPMC	IPMC/PVDF1	IPMC/PVDF2
W (mm)	7.3	8.2	7.6
L (mm)	37.2	36.0	33.0
H_1 (μm)	355	340	350.0
H_2 (μm)		30.0	100.0
H_3 (μm)		30.0	30.0
K_{mea} (N m^{-1})	0.906	2.283	4.676
K_{FEA} (N m^{-1})	0.908	2.286	4.647

The moment of inertia of each layer is

$$I_i = \frac{1}{12} W H_i^3 + W H_i d_i^2, \quad \text{for } i = 1, 2, 3. \quad (7)$$

From the moment balance equation [20],

$$M = \frac{\sum_{i=1}^3 E_i I_i}{\rho(x)} = F(L - x), \quad (8)$$

where $\rho(x)$ is the radius of curvature. For small bending, the radius of curvature can be given by

$$\frac{1}{\rho(x)} = \frac{d^2 z}{dx^2}, \quad (9)$$

where $z(x)$ denotes the deflection of the beam along the length x . With the boundary condition $z(0) = 0$ and $\dot{z}(0) = 0$, one gets

$$z(x) = \frac{F}{\sum_{i=1}^3 E_i I_i} \left(\frac{Lx^2}{2} - \frac{x^3}{6} \right). \quad (10)$$

Evaluating z at $x = L$ yields the expression of the spring constant

$$K = \frac{F}{z_{\text{max}}} = \left(\frac{3 \sum_{i=1}^3 E_i I_i}{L^3} \right). \quad (11)$$

Experiments were conducted to measure and compare the spring constants of the IPMC and IPMC/PVDF beams. The IPMC or IPMC/PVDF beam is clamped at one end and is pushed by the tip of a calibrated micro-force sensor which is mounted on a linear actuator. The sensitivity of the micro-force sensor is $9.09 \text{ mV } \mu\text{N}^{-1} \pm 6.5\%$ and its spring constant is 0.264 N m^{-1} . A laser displacement sensor measures the bending displacement of the beam z_{max} under the pushing

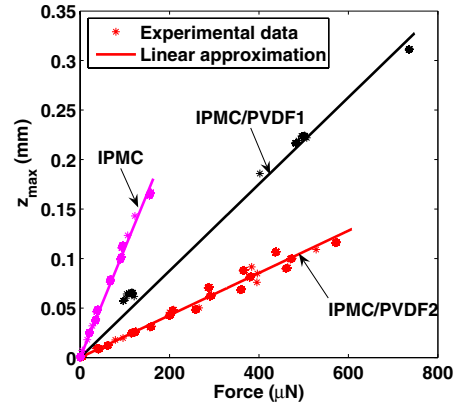


Figure 6. Spring constant of IPMC/PVDF beams.

force F . A $20\times$ microscope (FS60, Mitutoyo) is used to monitor the experiments. Figure 5(a) illustrates the diagram of the experimental setup, while figure 5(b) shows the actual picture. Measurements were conducted for an IPMC beam and two IPMC/PVDF beams which have insulating layers of different thickness (IPMC/PVDF1 and IPMC/PVDF2). Detailed beam dimensions can be found in table 1. Figure 6 shows the measured displacement versus force data and the linear approximations, from which the spring constants can be calculated. From the experimental data, the Young's moduli of individual layers can be identified using (11): $E_1 = 0.571 \text{ GPa}$, $E_2 = 0.73 \text{ GPa}$, $E_3 = 1.96 \text{ GPa}$. These values are within the ranges reported in the literature [21, 22].

To validate the linear analysis above, more accurate finite-element computation was conducted using CoventorWare⁵, where the identified parameters are used together with the given geometric dimensions. The spring constants are calculated based on the free-end deflection of beams when they are subjected to an external force $F = 20 \mu\text{N}$ at the tip. Table 1 lists the spring constants obtained through experimental measurement (K_{mea}) and finite element analysis (K_{FEA}), for the different beams. The close agreement between K_{mea} and K_{FEA} validates the model and analysis.

As shown in table 1, the thicker the insulator, the stiffer the IPMC/PVDF structure. In order to optimize the bending

⁵ <http://www.coventor.com>

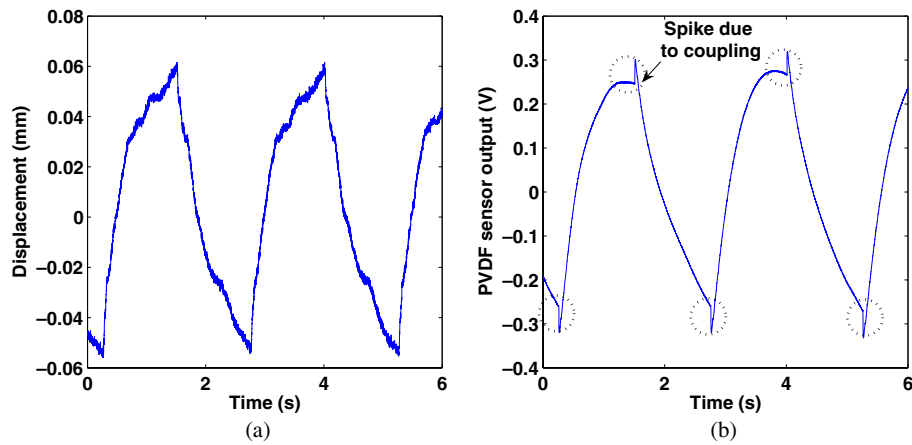


Figure 7. (a) Bending displacement detected by the laser sensor; (b) sensing output from the PVDF, showing the spikes from electrical feedthrough.

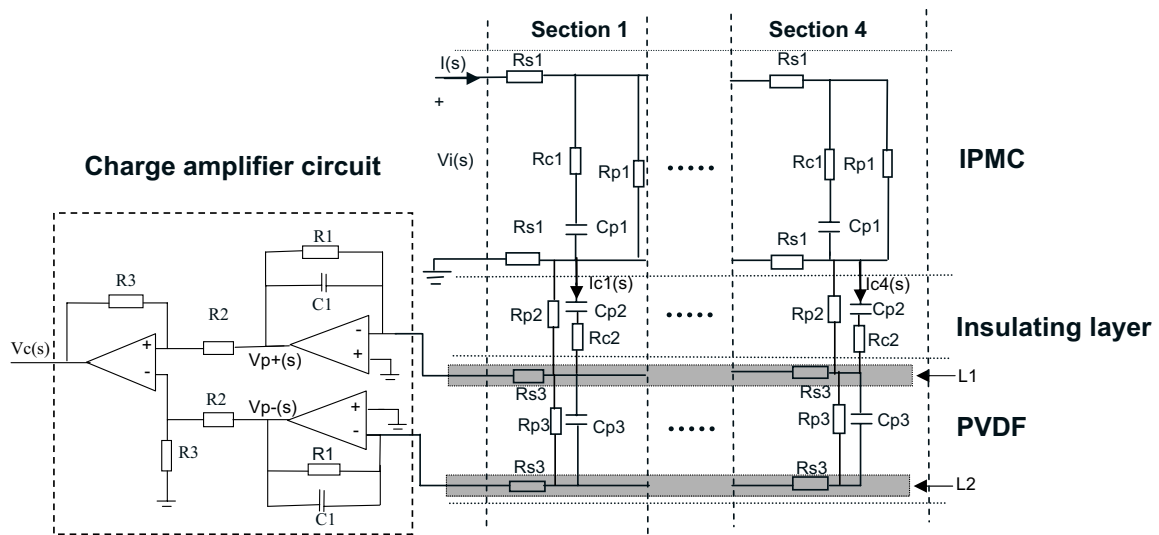


Figure 8. Circuit model of the IPMC/PVDF structure.

performance of the IPMC/PVDF structure, one should select the elastic insulating layer to be as soft and thin as possible. However, a thinner insulating layer may result in stronger electrical feedthrough coupling. In our design, the thickness of the insulating layer was chosen to be 30 μm to achieve tradeoff between the two considerations.

4. Electrical feedthrough coupling and model-based real-time compensation

4.1. The feedthrough coupling effect

Since the PVDF film is closely bonded to the IPMC with a very thin insulating PVC film, the coupling capacitance between the IPMC and the PVDF results in an electrical feedthrough effect during simultaneous actuation and sensing. When the actuation signal is applied to the IPMC, the actuation voltage generates coupling current going through the insulating layer and then induces a coupling charge on the PVDF. As a result, the charge amplifier gathers both the sensing and coupling charges from

the PVDF. The presence of feedthrough coupling is illustrated by applying a 0.4 Hz square-wave actuation input (peak-to-peak 1.4 V). In the experiment, the humidity was 34% and the temperature was 23 $^{\circ}\text{C}$. Figure 7(a) shows the bending displacement detected by the laser sensor, while figure 7(b) shows the output from the charge amplifier. The spikes in the PVDF sensor output arise from the capacitive coupling between the IPMC and PVDF layers when the actuation voltage jumps.

4.2. Modeling of the coupling effect

A complete circuit model of the IPMC/PVDF structure was developed to understand and capture the feedthrough coupling dynamics. As shown in figure 8, the model includes the equivalent circuits for individual layers and their natural couplings. Due to the non-negligible resistances resulting from the porous surface electrodes of the IPMC, the voltage potential is not uniform along the IPMC length. A distributed transmission-line type model is thus proposed. The overall

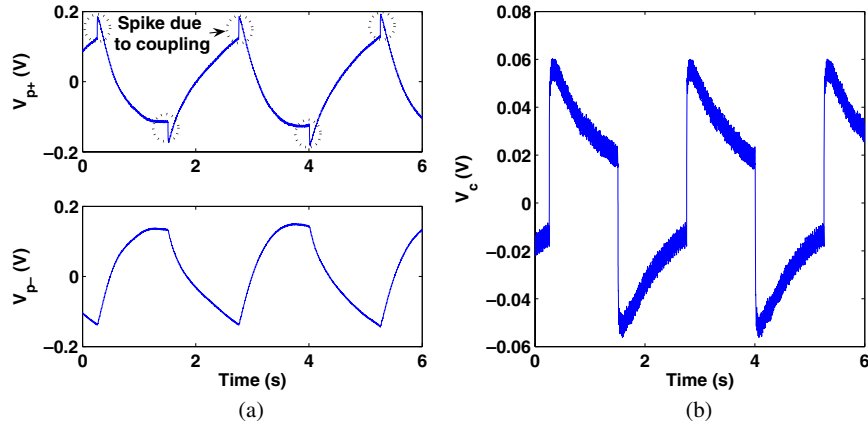


Figure 9. (a) V_{p+} , V_{p-} sensing signals; (b) extracted coupling signal V_c .

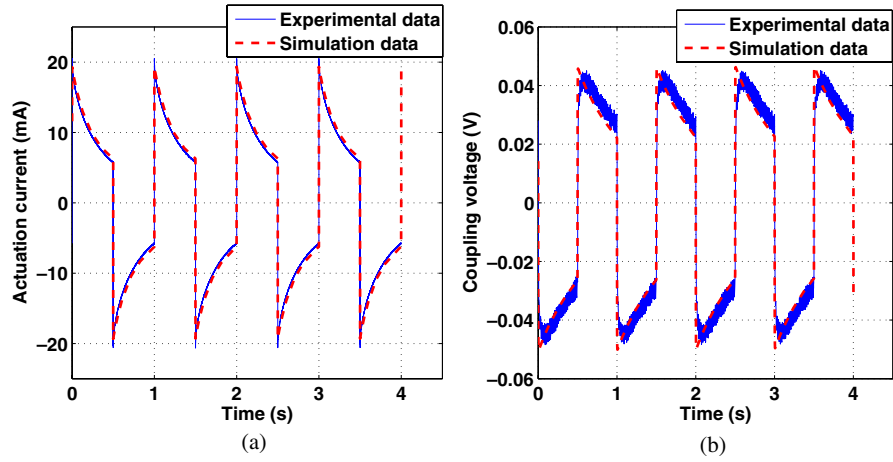


Figure 10. Comparison of model prediction and experimental measurement. (a) Actuation current; (b) coupling signal.

circuit model is broken into discrete elements along its length for parameter identification and simulation purposes. In this paper, the circuit model is chosen to have four sections of identical elements. The surface resistance of the IPMC is represented by R_{s1} , while other key electrodynamic processes (e.g., ionic transport, polymer polarization and internal resistances) are reflected in the shunt element consisting of resistor R_{c1} and capacitor C_{p1} . The polymer resistance is described by R_{p1} . In the circuit model of the insulating layer, R_{p2} , C_{p2} , R_{c2} are resistances and capacitances between the IPMC and PVDF. In the circuit model of the PVDF, R_{s3} is the surface resistance of the PVDF, and R_{p3} and C_{p3} represent the resistance and capacitance between the electrodes of the PVDF.

In order to identify the circuit parameters, the impedances are measured at multiple frequencies. The impedances of each layer are nonlinear functions of the resistances and capacitances involved. The parameters are identified using the Matlab command ‘nlinfit’, which estimates the coefficients of a nonlinear function using least squares. Table 2 lists the identified parameters.

The proposed circuit model will be validated by comparing its prediction of the feedthrough coupling signal with experimental measurement. We first explain a simple method for measuring the coupling signal. We observe that,

Table 2. Identified parameters in the circuit model.

	IPMC layer	Insulating layer	PVDF layer
R_{s1}	17 Ω	R_{p2} 500 M Ω	R_{s3} 0.1 Ω
R_{c1}	30 Ω	C_{p2} 42 pF	R_{p3} 600 M Ω
C_{p1}	3 mF	R_{c2} 4.5 M Ω	C_{p3} 290 pF
R_{p1}	25 k Ω		

due to the low surface resistance of the PVDF (see table 2), the electrode layer L_1 in figure 8 shields the coupling current from reaching the electrode layer L_2 . This means that the feedthrough coupling signal does not exist in V_{p-} , which is related to the charge from the layer L_2 . This statement is supported by the measurement, shown in figure 9(a), where spikes only appear in V_{p+} . Since only V_{p+} has a coupling component while the sensing components in V_{p-} and V_{p+} have a phase shift of 180° , the coupling signal is obtained as

$$V_c = V_{p+} + V_{p-}. \quad (12)$$

Figure 9(b) shows the extracted coupling signal.

Figure 10 compares the PSpice simulation results based on the circuit model with experimental results when a 1 Hz square-wave actuation voltage is applied. Good agreement is achieved for both the actuation current in the IPMC (figure 10(a)) and the coupling voltage V_c (figure 10(b)).

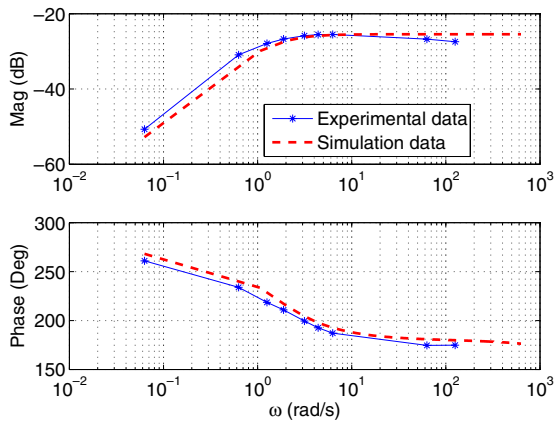


Figure 11. Verification of the coupling dynamics.

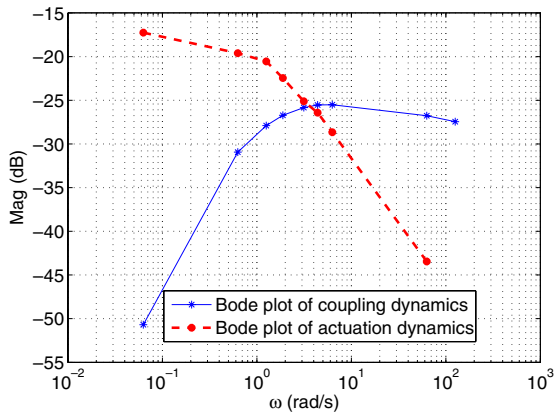


Figure 12. Bode plots of coupling dynamics and actuation dynamics.

The transfer function from the actuation voltage to the coupling voltage can be derived from the circuit model. Since there are 14 capacitors in the circuit model, the transfer function will be 14th order, which is not easy to implement in real time. After an order-reduction process, the transfer function of the coupling dynamics can be approximated by a fifth-order system:

$$T_c = \{- (509s^4 + 72s^3 + 1.5 \times 10^4s^2 + 2203s)\} \times \{(s^5 + 9525s^4 + 1.5 \times 10^4s^3 + 2.9 \times 10^5s^2 + 4.5 \times 10^5s + 6 \times 10^4)\}^{-1}. \tag{13}$$

To further verify the coupling model, a sequence of sinusoidal voltage signals with frequency ranging from 0.01 to 20 Hz are applied to the IPMC. Actuation voltages are measured and coupling signals are effectively extracted from V_{p+} and V_{p-} for the purpose of obtaining the empirical Bode plots of the coupling dynamics. Figure 11 shows that the Bode plots of the derived transfer function (13) match up well with the measured Bode plots.

4.3. Real-time compensation in simultaneous actuation and sensing

There are several possible schemes to get rid of the coupling signal. Inserting another conductive layer between the IPMC and PVDF to shield the feedthrough coupling is one potential solution, but at the cost of increased stiffness and fabrication complexity. Another solution is to just use V_{p-} as the sensing signal, but this single-mode sensing scheme is sensitive to the common-mode noise in practice. Since the coupling dynamics has high-pass characteristics, one might also try to eliminate the coupling component with low-pass filtering. However, the relatively low cut-off frequency of the coupling dynamics, compared to the actuation bandwidth (see figure 12), makes this approach infeasible.

In this paper, a model-based real-time compensation scheme is proposed to remove the feedthrough coupling component. The coupling charge is calculated from the coupling circuit model (13). By subtracting it from the measured charge of the PVDF, the sensing charge can be extracted. Figure 13 illustrates the compensation scheme. Figure 14 compares the displacement measurement obtained from the PVDF sensor with that from the laser sensor when a 0.4 Hz square-wave actuation input is applied. It is seen that the spike related to the electrical coupling is removed by the compensation scheme. Although there is about 12% error shown in figure 14, the amplitudes and the phases agree well. Investigation is under way to further improve the measurement accuracy of the PVDF sensor.

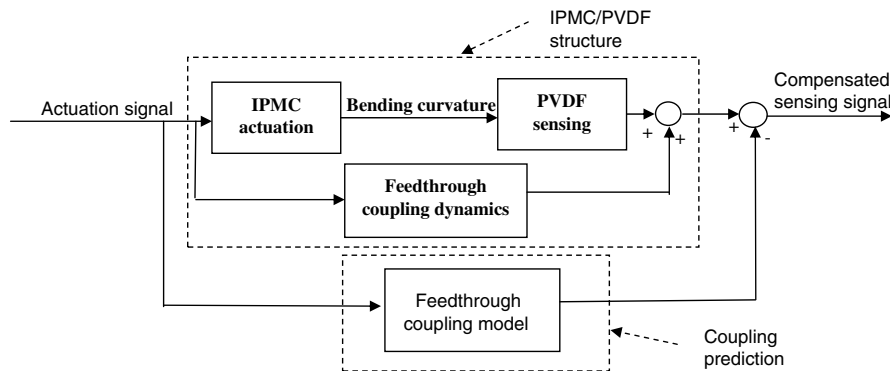


Figure 13. Diagram of the real-time compensation.

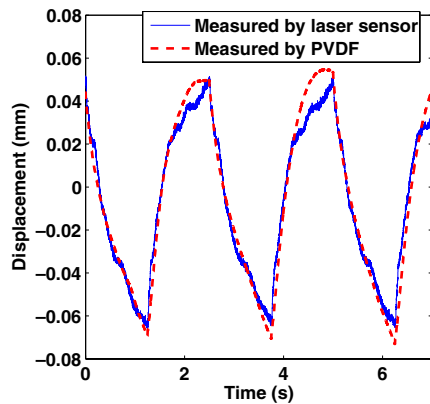


Figure 14. Comparison of displacement measurements by laser sensor and PVDF sensor.

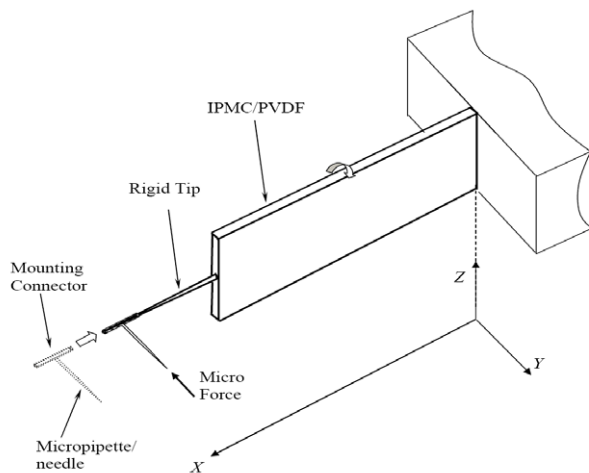


Figure 15. Illustration of the IPMC/PVDF micro-force injector.

5. Application to micro-injection of living *Drosophila* embryos

The developed IPMC/PVDF sensori-actuator was applied to the micro-injection of living *Drosophila* embryos. Such

operations are important in embryonic research for genetic modification. Currently this process is implemented manually, which is time-consuming and has a low success rate due to the lack of accurate control on the injection force, the position and the trajectory. The IPMC/PVDF structure is envisioned to provide accurate force and position control in the micro-injection of living embryos, and thus to automate this process with a high yield rate. In this study, an open-loop injection experiment with the IPMC/PVDF sensori-actuator was conducted, and the process of the injection behavior was captured by the PVDF sensor.

The developed IPMC/PVDF micro-force injector is illustrated in figure 15. A micro pipette with an ultra-sharp tip ($1.685 \mu\text{m}$ in diameter and 2.65° in angle) is mounted at the end point of a rigid tip attached to the IPMC/PVDF structure.

The *Drosophila* embryos were prepared as described in [23]. The dimensions of the embryos are variable, with an average length of $500 \mu\text{m}$ and a diameter of about $180 \mu\text{m}$. Figure 16(a) shows the diagram of the experimental setup for embryo injection, while figure 16(b) shows a photo. A 3D precision probe station (CAP-945, Signatone), which is controlled by a 3D joystick, moves the needle close to an embryo and then a ramp voltage, which starts from 0 V and saturates at 2 V, is applied to the IPMC. The IPMC drives the beam with the needle to approach the embryo. After the needle contacts the membrane of the embryo, the latter will be deformed but not penetrated due to its elasticity. At this stage, the needle is still moving until the reaction force between the needle and embryo reaches the penetration force. The needle stops at the penetration moment for a while (about 0.2 ms) due to temporary force balance. After that, the embryo membrane is penetrated and the needle moves freely into the embryo.

Figure 17(a) shows snapshots of the successful injection progress. Figure 17(b) shows the displacement of the needle detected both by the laser sensor and by the compensated PVDF sensing signal. It is concluded that the predicted displacement reflects the movement of the needle, and the process of injection can be monitored by the PVDF.

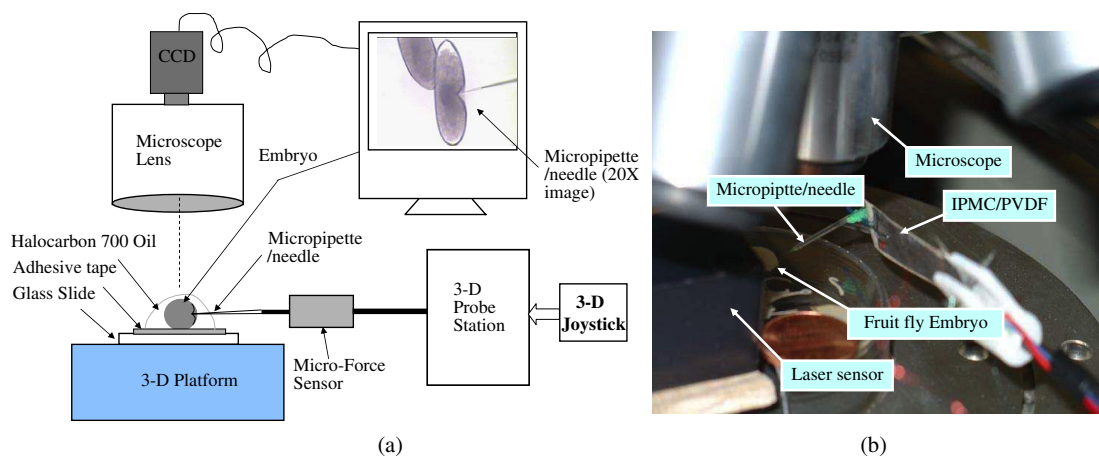


Figure 16. (a) Diagram of experimental setup for embryo injection; (b) picture of experimental setup.

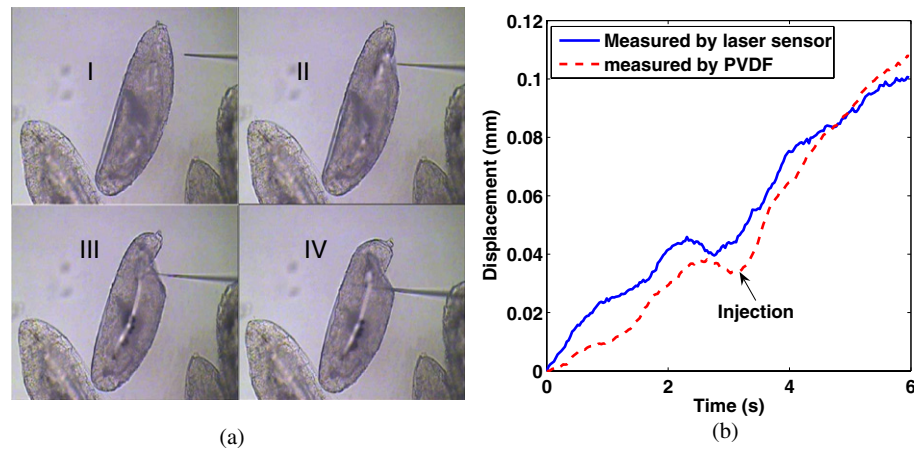


Figure 17. (a) Snapshots captured during the embryo injection; (b) bending displacement during the injection measured by both the laser sensor and the integrated PVDF sensor.

6. Conclusions and future work

In this paper, a novel hybrid IPMC/PVDF structure is developed for both micro sensing and actuation. The feedthrough coupling effect from actuation signal to sensing signal is addressed through optimization of the insulating layer thickness and model-based compensation. Experimental results demonstrate that the developed IPMC/PVDF sensori-actuator, together with the model-based compensation algorithm, can perform effective, simultaneous actuation and sensing. As the first application, the sensori-actuator has been successfully used for open-loop micro injection of *Drosophila* embryos. The penetration process is captured well by the compensated PVDF sensing signal.

The model-based compensation algorithm assumes a fixed model for feedthrough dynamics. For an IPMC based on water solvent, the feedthrough dynamics is expected to change with the hydration level of the IPMC. In other words, the coefficients in the model (13) will be time-varying. In this case recursive estimation methods [24] can be used to update the model online based on electrical measurement. On the other hand, if one uses an IPMC that has stable performance in air (based on a different solvent from water), compensation using a fixed model will suffice.

Ongoing research is focused on investigation of the nonlinear, dynamic behavior of PVDF as well as the thermal drift associated with the pyroelectric effect of PVDF, with a goal of improving the measurement accuracy of the PVDF sensor. The IPMC/PVDF configuration in this paper allows only the sensing of the bending displacement (or curvature). This will be extended to integrated sensing of both displacement and force output, which is of importance in numerous biological micromanipulation applications. Finally, feedback of the control of embryo injection will be studied to fully automate the process.

Acknowledgments

This research was supported in part by an NSF SGER grant (CMS 0550651), an NSF CAREER grant (ECS 0547131), MSU IRGP (05-IRGP-418), and a Summer Dissertation

Fellowship awarded to ZC by the MSU Graduate School and by Microsoft Inc. The contribution of Jason Malinak to the early-stage development of the IPMC/PVDF structure is also acknowledged. The authors would like to thank Mr Martin S Buckley and Miss Li Li at the Arnosit's Lab of the Department of Biochemistry & Molecular Biology, MSU, for their great effort in the preparation of fresh *Drosophila* embryos.

References

- [1] Bar-Cohen Y 2004 Electric flex *IEEE Spectrum* **41** (no 6) 29–33
- [2] Shahinpoor M and Kim K J 2001 Ionic polymer–metal composites: I. Fundamentals *Smart Mater. Struct.* **10** 819–33
- [3] Guo S, Fukuda T and Asaka K 2003 A new type of fish-like underwater microrobot *IEEE/ASME Trans. Mechatron.* **8** 136–41
- [4] Kim B, Ryu J, Jeong Y, Tak Y, Kim B and Park J-O 2003 A ciliary based 8-legged walking micro robot using cast IPMC actuators *Proc. IEEE Int. Conf. on Robots and Automation* pp 2940–5
- [5] Guo S, Fukuda T, Kosuge K, Arai F and Negoro M 1995 Micro catheter system with active guide wire *Proc. IEEE Int. Conf. on Robotics and Automation* pp 79–84
- [6] Bar-Cohen Y, Leary S, Shahinpoor M, Harrison J O and Smith J 1999 Flexible low-mass devices and mechanisms actuated by electroactive polymers *Smart Structures and Materials 1999: Electroactive Polymer Actuators and Devices, Proc. SPIE* **3669** 51–6
- [7] Tadokoro S, Yamagami S and Ozawa M 1999 Soft micromanipulation device with multiple degrees of freedom consisting of high polymer gel actuators *Proc. IEEE Int. Conf. on Micro Electro Mechanical Systems* pp 37–42
- [8] Lumia R and Shahinpoor M 1999 Microgripper design using electroactive polymers *Smart Structures and Materials 1999: Electroactive Polymer Actuators and Devices* pp 322–9
- [9] Dosch J, Inman D and Garcia E 1992 A self-sensing piezoelectric actuator for collocated control *J. Intell. Mater. Syst. Struct.* **3** 166–85
- [10] Bonomo C, Negro C D, Fortuna L, Graziani S and Mazza D 2003 Characterization of IPMC strip sensorial properties: preliminary results *Proc. Int. Symp. on Circuits and Systems* pp IV-816–9
- [11] Farinholt K and Leo D 2004 Modeling of electromechanical charge sensing in ionic polymer transducers *Mech. Mater.* **36** 421–33

- [12] Newbury K M 2002 Characterization, modeling, and control of ionic polymer transducers *PhD Dissertation* Virginia Polytechnic Institute and State University
- [13] Measurement Specialties 1998 *Piezo Film Sensors Technical Manual* Hampton, VA
- [14] Lam K Y and Ng T 1999 Active control of composite plates with integrated piezoelectric sensors and actuators under various dynamic loading conditions *Smart Mater. Struct.* **8** 223–37
- [15] Lee Y-S, Elliot S J and Gardonio P 2003 Matched piezoelectric double sensor/actuator pairs for beam motion control *Smart Mater. Struct.* **12** 541–8
- [16] Wieschaus E 1997 From molecular patterns to morphogenesis: the lessons from *Drosophila* *Nobel Lectures, Physiology or Medicine 1991–1995* ed N Ringertz (Singapore: World Scientific)
- [17] Measurement Specialties 1999 *Piezo Film Sensors Technical Manual* Hampton, VA
- [18] Bennett M D and Leo D 2004 Ionic liquids as stable solvents for ionic polymer transducers *Sensors Actuators A* **115** 79–90
- [19] Shen Y, Xi N, Wejinya U and Li W 2004 High sensitivity 2D force sensor for assembly of surface MEMS devices *Proc. IEEE/RSJ Int. Conf. on Intelligent Robots and Systems (Sendai, Japan)* pp 3363–8
- [20] Gere J M and Timoshenko S 1997 *Mechanics of Materials* 4th edn (Boston, MA: PWS Publishing Company)
- [21] Siripong M, Fredholm S, Nguyen Q, Shih B, Itescu J and Stolk J 2006 A cost-effective fabrication method for ionic polymer–metal composites *Electroresponsive Polymers and Their Applications (MRS Symp. Proc. vol 889)* ed V Bharti, Y Bar-Cohen, Z Cheng, Q Zhang and J Madden (Warrendale, PA: Materials Research Society) p 0889–W04–03
- [22] Sakakibara T, Izu H, Kura T, Shinohara W, Iwata H, Kiyama S and Tsuda S 1994 Development of high-voltage photovoltaic micro-devices for an energy supply to micromachines *Proc. IEEE 5th Int. Symp. on Micro Machine and Human Science (Nagoya, Japan)* pp 71–6
- [23] Shen Y, Wejinya U C, Xi N, Buckley M S, Pomeroy C A and Arhosti D N 2007 Force measurement and mechanical characterization of living *Drosophila* embryos for human medical study *J. Eng. Med.* at press
- [24] Astrom K J and Wittenmark B 1995 *Adaptive Control* 2nd edn (Reading, MA: Addison-Wesley)